

Progressive technologies of electrophysical treatment for regulation of stress-strain states of elements of welded structures

L. Lobanov¹ • P. Ustyomenko² • Yu. Sydorenko² • M. Pashchyn¹

Received: 9 February 2023 / Revised: 24 March 2023 / Accepted: 30 March 2023

Abstract. The development of industry stimulates the development of modern approaches to the optimization of welded structures. The use of pulsed electromagnetic fields, plasma currents, electrodynamic forces and their combined effects is a new trend in engineering practice to improve the mechanical characteristics of metal materials and welded joints (WJ). Treatment with a pulsed electromagnetic field (TwPEMF) is a promising direction for optimizing the stress-strain states (SSS) of welded structures made of non-ferromagnetic metal materials. Using the method of electronic speckle interferometry, the effect of TwPEMF on the SSS of specimens of circumferential WJ with a thickness of $\delta = 1.0$ mm from aluminium AMg6 alloy was investigated. Based on the original procedure using an accelerometer, the kinetics of the action of the force P of the magnetic field pressure on the residual displacements f and SSS of the specimens during their TwPEMF were investigated. TwPEMF of WJ specimens was performed without and with the use of an additional shield made of AMg6 alloy $\delta = 5.0$ mm. It was found that the use of a shield increases the amplitude values of force P by up to two times, which is caused by an increase in the active volume of the conductive medium. At the same time, TwPEMF without and with the use of a shield contributes to the reduction of f values by 2 and 4 times, respectively, and residual SSS by 50 and 80%. On the basis of mathematical modelling, the advantages of using electrodynamic treatment (EDT) of butt WJ $\delta = 3.0$ mm of AMg61 (1561) alloy in the TIG welding process compared to EDT at room temperature (T_k) are substantiated. According to the results of the model verification, it was proved that EDT during TIG contributes to the formation of peak values of residual compressive stresses in the weld zone by 60% more than EDT during T_k . The use of a pulsed barrier discharge (PBD), which generates a low-temperature plasma on the surface of the metal being treated, contributes to the optimization of its structure. An increase in the hardness HV of structural 25KhGNMT steel as a result of its PBD treatment from 420 to 510 units was established, which is accompanied by the dispersion of the metal microstructure.

Keywords: treatment of welded joints; pulsed magnetic field; pulsed barrier discharge; electrodynamic treatment; aluminium alloy; structural steel; residual displacements; stress-strain state; hardness of steel.

Introduction

The development of modern industry requires the study of progressive energy-saving technologies to improve the service properties of metal structures. In this regard, the development of methods of treatment of metal

materials and welded joints based on the effect of a pulsed electromagnetic field is challenging. These include electrodynamic treatment (EDT), treatment with a direct action (pressure) of a pulsed electromagnetic field (TwPEMF) and a pulsed barrier discharge (PBD) [1–6]. Based on EDT and TwPEMF, technologies for control of the stress-strain state of thin-sheet welded joints are developed. Taking into account the results [1], a promising technology of EDT in the process of welding has been developed, which provides the following advantages over EDT after welding: 1) effect of the thermal cycle of welding contributes to more intensive relaxation of welding stresses as a result of EDT compared to treatment of weld metal at room temperature; 2) reduction in the labour intensity of manufacturing welded structure due to the transition from successive to simultaneous performance of technological operations of welding

✉ L. Lobanov

lobanov@nas.gov.ua

✉ Yu. Sydorenko

yura_michael@ukr.net

¹ E. O. Paton Electric Welding Institute of the National Academy of Sciences of Ukraine, Kyiv, Ukraine

² Igor Sikorsky Kyiv Polytechnic Institute, Kyiv, Ukraine

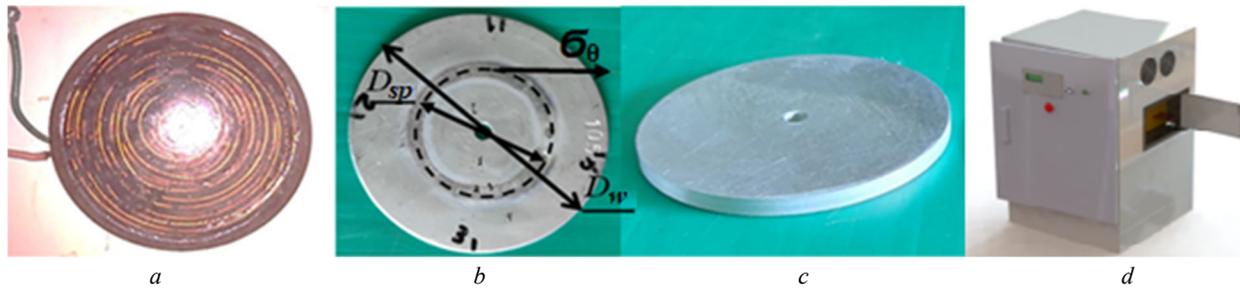


Fig. 1. Appearance: *a*) plane inductor; *b*) specimen of circumferential welded joint of AMg6 alloy with a thickness $\delta = 1.0$ mm, where $D_{sp} = 90$ mm and $D_w = 45$ mm are respectively the diameters of the specimen and the weld, σ_θ is the component of residual stresses; *c*) current-conducting shield with a diameter of 90 mm and a thickness of 5 mm; *d*) PS for TwPEMF

and EDT. The use of PBD opens up new opportunities to improve the hardness of structural steels for special equipment.

Aim of the work is the study of TwPEMF, EDT and PBD effect on residual stresses and mechanical characteristics of metal materials and welded joints.

Research procedure and materials

Electrophysical models, which form the basis of the action of TwPEMF, EDT and PBD on metals, alloys and welded joints, are presented respectively in [4], [1] and [6]. Electrophysical characteristics of electrode systems and power sources for TwPEMF, EDT and PBD are presented, respectively, in [2, 4, 5], [1, 3] and [6]

As a tool for TwPEMF realization, a plane inductor (Fig. 1 *a*) was used, and to evaluate the efficiency of treatment, plane specimens of AMg6 aluminium alloy in the form of a disc were used, whose thickness and diameter were respectively $\delta = 1.0$ mm and $D_{sp} = 90$ mm (Fig. 1 *b*).

During treatment, a current-conducting shield in the form of a disc from AMg6 alloy was used, its diameter and thickness were respectively 90 and 5.0 mm (Fig. 1 *c*). Circumferential welds were produced by TIG method in Ar environment along the line of the circle with a diameter $D_w = 45$ mm. A tangent component σ_θ (Fig. 1 *b*) of residual stressed state of welded joints and vertical movements f of the discs' edges before and after TwPEMF were evaluated by the method of electron and speckle-interferometry.

To realize the discharge cycles of TwPEMF, the power source (PS) was used based on a capacitor system with a charging voltage U of up to 800 V and pulsed current amplitude of up to 10 kA (Fig. 1 *d*). PS can perform TwPEMF in an automatic mode with 1–5 s time periods between the pulses. The registration of time distributions of the pulsed current I and the power of electrodynamic pressure P at TwPEMF of the specimens without and with the use of a shield was performed using a non-induction shunt and an accelerometer Kistler Instrumente AG, respectively [7]. TwPEMF was performed on the specimens with the thickness $\delta = 1.0$ mm and on the assembly of the specimen $\delta = 1.0$ mm with a current-conducting shield

$\delta = 5.0$ mm ($\sum \delta = 6$ mm). Treatment was carried out by the series of EPC on the mode at a charging voltage U of up to 800 V. Residual stressed states of welded joints were studied using the electron and speckle-interferometry method [1].

The hardware complex for automatic welding of aluminium alloys in the EDT process has been developed and manufactured (Fig. 2). The complex includes system for feeding filler wire 1, torch 2 for TIG welding, electrode device for EDT 3 and linear solenoid for movement 4 of electrode for EDT. The components of the complex are structurally combined into a monoblock.

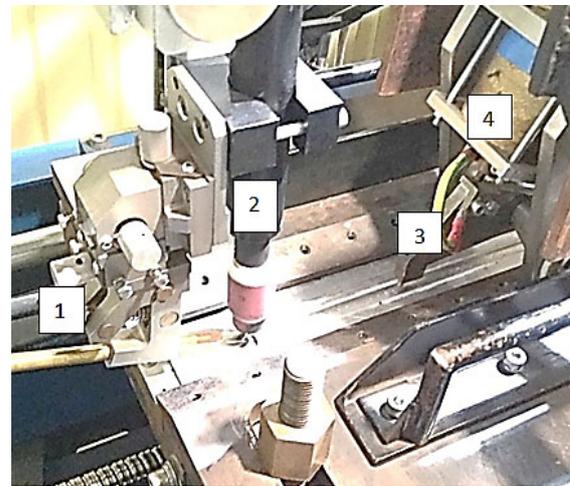


Fig. 2. Hardware complex for automatic TIG welding, which is compatible with EDT of a weld, where 1 – system for feeding filler wire, 2 – welding torch, 3 – electrode device, 4 – linear solenoid for movement of EDT electrode

Mathematical modelling of stress-strain states of welded joints as a result of EDT was performed in the conditions of elevated temperatures (in the process of welding), with the use of a simplified two-dimensional (2D) planar formulation. The design diagram of the problem of the process of impact interaction of the electrode-indenter with plates [8] is presented in Fig. 3. The solution of the problem was performed using ANSYS/LS-DYNA software.

PBD treatment of the surface of specimens of 25KhGNMT steel was performed using an electrode system (ES), the structural diagram of which is shown in Fig. 4.

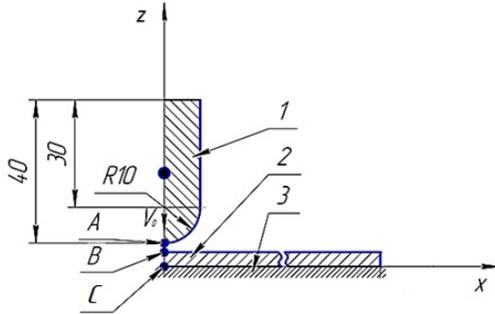


Fig. 3. Design diagram of the process of dynamic loading of a plate at EDT: 1 – electrode-indenter; 2 – specimen being treated; 3 – absolutely rigid base, A – point on the outer surface of the electrode-indenter, B – point on the outer surface of a plate, C – point on the back surface of a plate, V_0 – speed of movement of the electrode-indenter

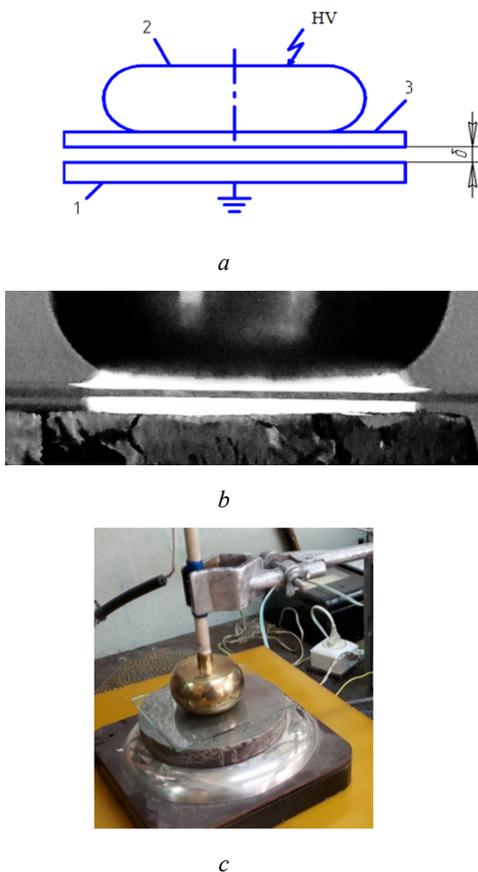


Fig. 4. PBD treatment of 25KhGNMT steel, where: a) diagram of electrode system for PBD treatment of specimens of 25KhGNMT steel, where 1 – studied specimen 1 of 25KhGNMT steel, 2 – high-voltage electrode, 3 – dielectric barrier, δ – gas gap, HV – high voltage; b) appearance of PBD; c) appearance of PBD treatment process of 25KhGNMT steel

The diagram of the electrode system (ES) for PBD treatment is shown in Fig.4 a. ES consisted of studied specimen 1 of 25KhGNMT steel, high-voltage electrode 2 and glass (quartz glass) dielectric barrier 3 ($100 \times 100 \times 1 \text{ mm}^3$). To reduce the edge effect, electrode 2 had rounded edges. The treatment was carried out at a gas gap δ of 1mm thickness between plate 1 and barrier 3. High voltage (HV) was supplied to electrode 2 from the pulse generator (PG), which provided unipolar pulses of a voltage with an amplitude of up to 30 kV at their rising rate $\approx 3 \cdot 10^{11} \text{ V/s}$ and a duration of about 150 ns. The appearance of the discharge, shown in Fig.4 b (exposure time is 0.1 s) indicates a homogeneous nature in the gap δ rather than filamentous.

Discussion of research results

Dependence of pressure force P at TwPEMF on current I for different thickness δ of the specimens is shown in Fig. 5. Based on its data, in the studied range of treatment modes, it is possible to see that with an increase in δ , P will grow, because it is defined as an integral value in a certain volume of a current-conductive medium. At an increase in δ to 6.0 mm as a result of using a shield (curve 2), the values P rise twice compared to TwPEMF of the specimens $\delta = 1.0 \text{ mm}$ without a shield (curve 1).

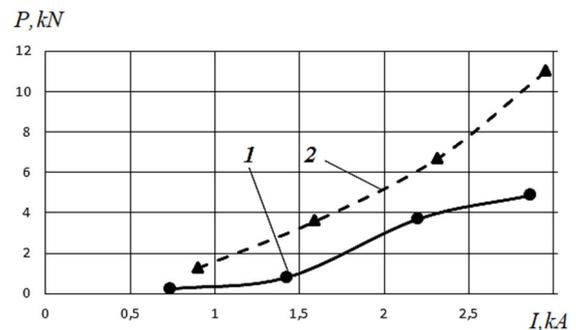


Fig. 5. Influence of amplitude EPC values – I on pressure force P at TwPEMF of specimens of circumferential welded joints $\delta = 1.0 \text{ mm}$ of AMg6 alloy, curve 1 – TwPEMF without a shield, curve 2 – TwPEMF with a shield

The efficiency of TwPEMF effect on the residual forming of the specimens treated under the abovementioned conditions confirm the data given in Fig. 4 a–c. The values of vertical movements of the discs’ edges f (Fig. 6 a) were recorded at the points Nos. 1–4 (Fig. 6 c) with a fixed angular distance l_α of 90° between the adjacent points. Performance of TwPEMF without a shield (Fig. 6 d, curve 2) and with its use (curve 3) allows reducing the values of movements f of the discs’ edges relatively by up to two or eight times compared to the specimens that were not subjected to TwPEMF.

Fig. 7 shows the results of TwPEMF effect on the component σ_θ of residual stresses in the centre of the weld

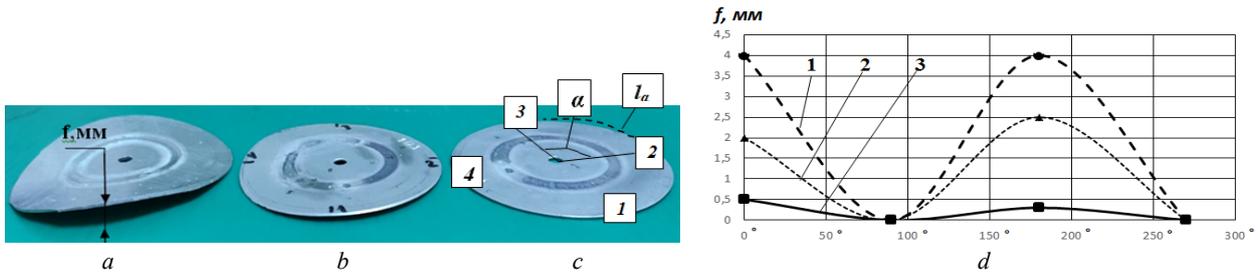


Fig. 6. Residual forming of circumferential welded joints of AMg6 alloy, where: *a*) appearance (A) of the disc without treatment, where *f* is the movement of the disc's edges; *b*) A after TwPEMF without a shield; *c*) A after TwPEMF with a shield, where 1–4 is the number of point of movements measurement, α and l_α are respectively the angle and angular distance between the points 2–3; *d*) vertical movements *f* of the disc's edges, where curve 1 – without TwPEMF, 2 – after TwPEMF without a shield, 3 – after TWPEMF with the use of a shield

(W) and in the area around the weld (AAW) at a distance of 10 mm from the weld line. Taking into account the bending of the discs (Fig. 6), which results in the imbalance of the diagrams of residual stresses, as an evaluation of TwPEMF effect on the stressed state, the peak values σ_θ were determined in W and in AAW in the specimens in the original state and under the set treatment conditions. It is possible to see that in general TwPEMF has a positive effect on the residual stressed state of the circumferential welded joints of AMg6 alloy with a thickness $\delta = 1$ mm.

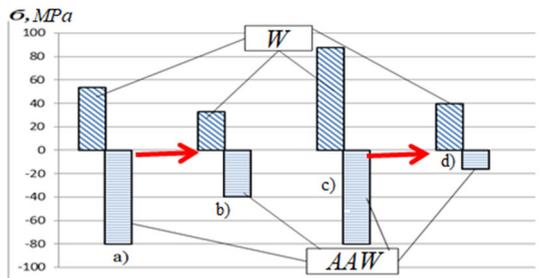


Fig. 7. Influence of TwPEMF on the component σ_θ of residual stresses in the welds (W) and in the area around the weld (AAW) of circumferential welded joints of the specimens of AMg6 alloy with a thickness $\delta = 1$ mm: *a*) peak values σ_θ of the specimens in the initial state; *b*) σ_θ after TwPEMF without the use of a shield; *c*) σ_θ specimens in the initial state; *d*) σ_θ after TwPEMF with the use of a shield

Though initial (before TwPEMF) values σ_θ during treatment without a shield – *a*) and with a shield – *c*) differ, which is associated with a low rigidity of the discs, it can be seen that the use of a shield has a positive effect on relaxation of stresses in TwPEMF. This is confirmed by comparing the diagrams between each other *a*–*b*) and *c*–*d*). Thus, the treatment without and with the use of a shield led to a decrease in the initial values σ_θ in the active zone of tension (W) respectively by 36 and 56%, and in the zone of reactive compression (AAW) – by 50 and 80%.

The results of mathematical modelling are shown in Fig. 8 from which it can be seen that EDT in the conditions of heating the plate from AMg61 alloy to the temperature

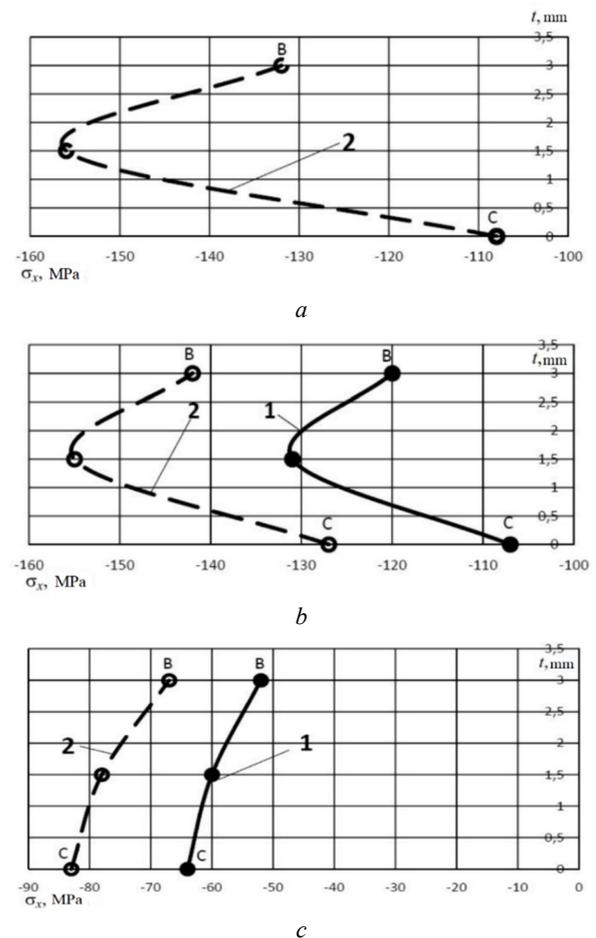


Fig. 8. Results of modelling stresses σ_x along the line between the points B and C (Fig. 3) of the plates of AMg61 alloy $\delta = 3$ mm after EDT at the temperature *T* and cooling to $T = 20^\circ\text{C}$, where curve 1 – σ_x (instant) at the moment of completion of contact interaction at elevated temperatures, curve 2 – σ_x at room temperature: *a*) $T = 20^\circ\text{C}$; *b*) $T = 150^\circ\text{C}$; *c*) $T = 300^\circ\text{C}$

$T = 150^{\circ}\text{C}$ (thermoelasticity), provides larger values of longitudinal (along the axis X in Fig. 3) compression σ_x stresses, than at $T = 20^{\circ}\text{C}$ (room) and at $T = 300^{\circ}\text{C}$ (thermoelasticity). This allows choosing the distance between welding torch 2 and electrode 3 for EDT (Fig. 2) that provides the optimum level of residual compression σ_x in the welded joint.

Verification of modelling results was carried out on the specimens of butt joints from AMg61 alloy with the sizes of $300 \times 200 \times 3$ mm (Fig. 9), where the Specimen No.1 was not subjected to EDT, the Specimen No.2 was subjected to EDT at $T = 20^{\circ}\text{C}$ and the Specimen No.3 was subjected to EDT at $T = 150^{\circ}\text{C}$. The values of residual longitudinal deflections f_x of the specimens and residual σ_x confirm both the efficiency of EDT, as well as its growth in the conditions of thermal deformation welding cycle. In the Specimen No.2, the values f_x are reduced by 1.8 times compared to the Specimen No.1, and in the Specimen No.3 – by 3.7 (Fig. 9 a). The values of the membrane tensile σ_x (curve 2 in Fig. 9, b–d) in the weld centre on the Specimen No.2 compared to the Specimen No.1 are reduced by 95% (Fig. 9 c), and in the Specimen No.3 they are transformed into compression and amount to about $0.3 \sigma_{0.2}$ for AMg61 alloy (Fig. 9 d).

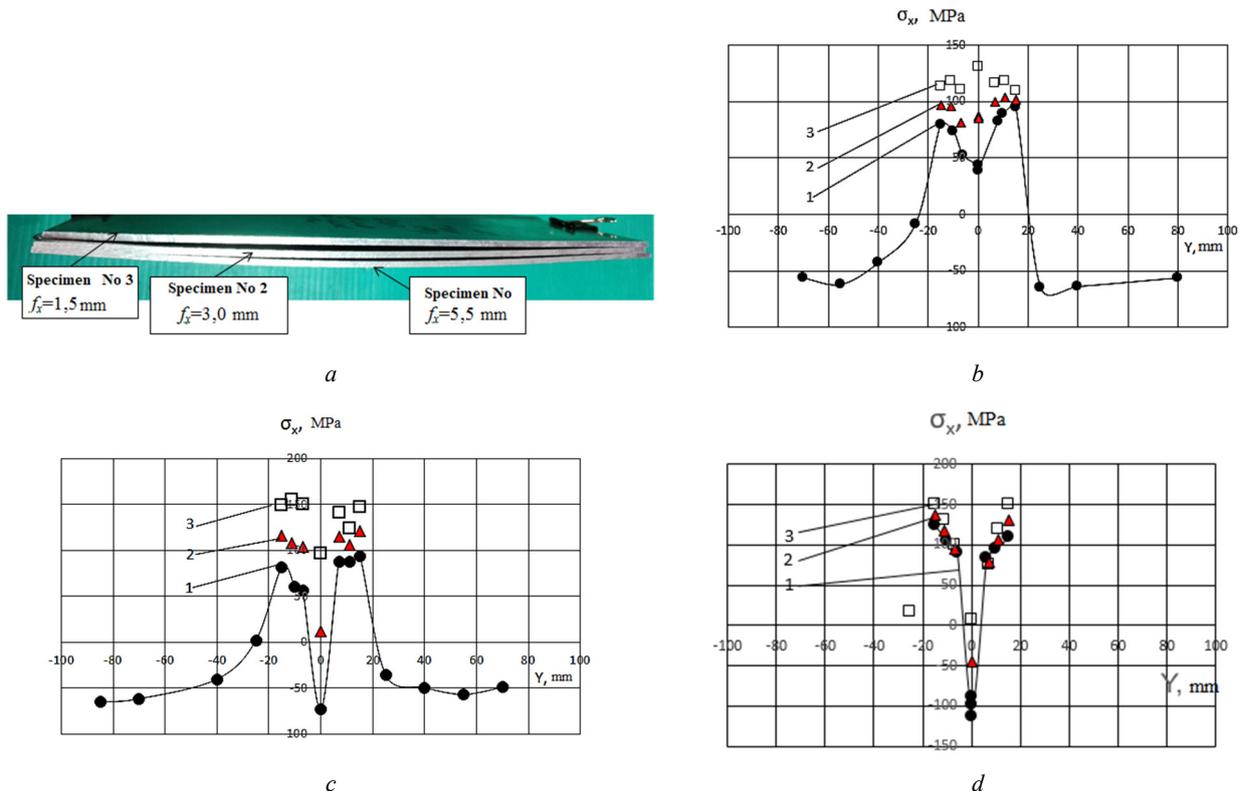


Fig. 9. Longitudinal deflections f_x and residual stresses σ_x of the specimens of welded joints of AMg61 alloy of $\delta = 3$ mm, where the Specimen No.1 – no EDT, Specimen No.2 – EDT at $T = 20^{\circ}\text{C}$, Specimen No.3 – EDT at $T = 150^{\circ}\text{C}$: a) appearance and values of f_x of the Specimens Nos.1...3; b) distribution of σ_x at the central cross-section of the Specimen No.1, where curve 1 – top (\bullet) surface of the point B in Fig. 3, curve, 2 – membrane stresses, 3 – bottom (\square) surface of the point B in Fig. 3; c) similarly to b) for the Specimen No.2; d) similarly to b) for the Specimen No.3

It was found that the maximum effect of PBD on the hardness of 25KhGNMT steel is achieved when duration of the specimens treatment is 15 minutes (at the optimal mode). In this case, the values of HV hardness after the treatment increase by 20% from 420 to 505 kg/mm² (Fig. 10 a). In depth from the treated surface (from 0 to 2200 μm) in the cross-section of the specimen, the changes in structural and phase composition, parameters of thin structure and dislocations density were revealed. In depth from the treated surface to 300 μm , exclusively the structure of tempered martensite and lower bainite is formed during its refinement and a uniform distribution of dislocations density $\rho = (2 \dots 8) \times 10^{10} \text{ cm}^{-2}$ (Fig. 10 b). The obtained results indicate that PBD facilitates an improvement in the dynamic strength of welded structures of the mentioned steel during their contact interactions.

Fig. 10. Influence of PBD treatment on the structure of 25KhGNMT steel: a) values of Vickers hardness (HV) before and after PBD treatment; thin structure before and after PBD treatment: b) tempered martensite (Mtemp) before and after PBD treatment, c) lower bainite (BI) before and after PBD

Analyzing the abovementioned results, it should be noted that TwPEMF, EDT in the process of welding and

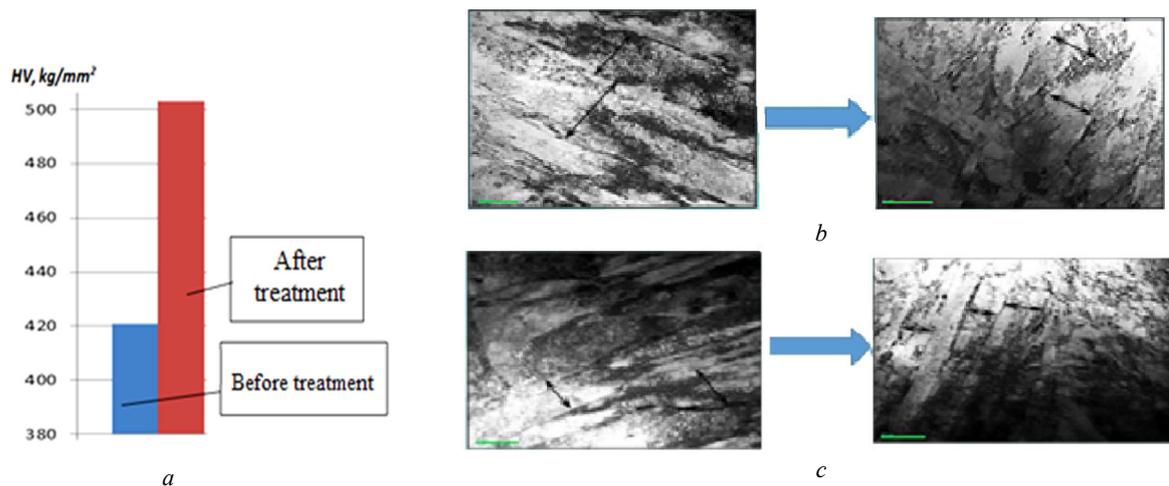


Fig. 10. Influence of PBD treatment on the structure of 25KhGNMT steel: *a*) values of Vickers hardness (*HV*) before and after PBD treatment; thin structure before and after PBD treatment: *b*) tempered martensite (Mtemp) before and after PBD treatment, *c*) lower bainite (BI) before and after PBD

local PBD treatment of metals, alloys and welded joints is the basis for the development of a number of technologies aimed at optimizing welded structures of new equipment.

Conclusions

1. It was found that treatment with a pulsed electromagnetic field (TwPEMF) allows reducing residual displacements and stresses of the specimens of circumferential welded joints from AMg6 alloy by up to eight times compared to untreated ones.

2. On the basis of mathematical modelling and experimental studies, it was proved that the use of electrodynamic treatment (EDT) of weld metal, which is performed in a single process synchronously with arc welding is more effective compared to separate EDT after welding, which is expressed in a more optimal residual stress-strain state of a finished welded joint of the aluminium AMg61 alloy.

3. It was found that as a result of treatment of 25KhGNMT steel with a pulsed barrier discharge (PBD), its Vickers hardness (*HV*) is increased by 20% – from 420 to 505 kg/mm², which spreads to a depth of up to 2 mm and is accompanied by dispersion of the treated structure.

References

- [1] L. Lobanov *et al.*, “Development of Post-weld Electrodynamic Treatment Using Electric Current Pulses for Control of Stress-Strain States and Improvement of Life of Welded Structures”, *Materials Performance and Characterization*, Vol. 7, No. 4, pp. 941–955, 2018. DOI: 10.1520/MPC20170092
- [2] V.I. Dubodelov and M.S. Goruk, “The use of electromagnetic fields and magnetodynamic phenomena to intensify the effect on metal systems: world and Ukrainian experience”, in *Materials Science: Achievements and Prospects*, Vol. 2, Kyiv, Akademperiodyka, 2018, pp. 24–50.
- [3] Y.M. Sydorenko *et al.*, “Stress-Strain State of Welded Joints of AMg6 Alloy after Electrodynamic Treatment During Welding”, *Strength of Materials*, Vol. 54, No. 6, pp. 983–996, 2022. DOI: 10.1007/s11223-023-00474-y
- [4] O.V. Cherkashyn *et al.*, “Pulsed Electromagnetic Field Effect on Residual Stresses and Strains of Welded Joints of AMg6 Aluminum Alloy”, *Strength of Materials*, Vol. 53, No. 6, pp. 834–841, 2021. DOI: 10.1007/s11223-022-00350-1
- [5] O.L. Mikhodui *et al.*, “Influence of Pulsed Electromagnetic Field Treatment on the Stressed State of AMg6 Aluminum”, *Materials Science*, No. 57, pp. 1–8, 2021. DOI: 10.1007/s11003-021-00507-4
- [6] I.V. Bozhko *et al.*, “Treatment of steel 25KHGNMT by acting on its surface with a pulsed barrier discharge”, *Tekhnichna elektrodynamika*, No. 1, pp. 76–80, 2023. DOI: 10.15407/tecned2023.01.076.
- [7] Kistler Instrumente AG. *Quartz Accelerometer 8042*.
- [8] M. O. Pashchyn *et al.*, “Modeling of stress-strain states of AMg6 alloy due to impact action of electrode-indenter in electrodynamic treatment”, *The Paton Welding J.*, No. 6, pp. 2–11, 2021. DOI: 10.37434/tpwj2021.06.01

Прогресивні технології електрофізичної обробки для регулювання напружено-деформованих станів елементів зварних конструкцій

Л.М. Лобанов¹, П.Р. Устименко², Ю.М. Сидоренко², М.О. Пащин¹

¹ Інститут електрозварювання ім. Є.О. Патона НАН України, Київ, Україна

² КПІ ім. Ігоря Сікорського, Київ, Україна

Анотація. Розвиток промисловості стимулює розробку сучасних підходів до оптимізації зварних конструкцій. Використання імпульсних електромагнітних полів, струмів плазми, електродинамічних сил та їх комбінованих впливів є новим трендом інженерної практики для підвищення механічних характеристик металевих матеріалів і зварних з'єднань (ЗЗ). Обробка імпульсним електромагнітним полем (ОІЕМП) ЗЗ є перспективним напрямком оптимізації напружено-деформованих станів (НДС) зварних конструкцій із неферомагнітних металевих матеріалів. Із застосуванням методу електронної спеклінтерферометрії досліджено вплив ОІЕМП на НДС зразків кільцевих ЗЗ товщиною $\delta = 1,0$ мм із алюмінієвого сплаву АМгб. На базі оригінальної методики із застосуванням датчика прискорень досліджено кінетику дії сили P тиску магнітного поля на залишкові переміщення f і НДС зразків при їх ОІЕМП. Виконували ОІЕМП зразків ЗЗ без та із застосуванням додаткового екрану зі сплаву АМгб $\delta = 5,0$ мм. Встановлено, що застосування екрану підвищує амплітудні значення сили P до двох разів, що зумовлено збільшенням активного об'єму електропровідного середовища. При тому ОІЕМП без та із застосуванням екрану сприяє зниженню значень f відповідно у 2 і 4 рази, а залишкових НДС – на 50 і 80%. На базі математичного моделювання обґрунтовано переваги застосування електродинамічної обробки (ЕДО) стикових ЗЗ $\delta = 3,0$ мм зі сплаву АМгб1 (1561) в процесі зварювання ТІГ у порівнянні із ЕДО при кімнатній температурі (T_k). По результатах верифікації моделі доведено, що ЕДО при ТІГ сприяє формуванню пікових значень залишкових напружень стискування в зоні зварного шва на 60% більше, ніж ЕДО при T_k . Застосування імпульсного бар'єрного розряду (ІБР), який генерує низькотемпературну плазму на поверхні металу, що обробляється, сприяє оптимізації його структури. Встановлено зростання твердості НV конструктивної сталі 25ХГНМТ в результаті її обробки ІБР із 420 до 510 одиниць, яке супроводжується диспергуванням мікроструктури металу.

Ключові слова: обробка зварних з'єднань; імпульсне магнітне поле; імпульсний бар'єрний розряд; електродинамічна обробка; алюмінієвий сплав; конструктивна сталь; залишкові переміщення; напружено-деформований стан; твердість сталі.